

SIMULATION OF RADIATION ATTENUATION IN POLYMER MATRIX COMPOSITE WITH EPOXY RESIN, REINFORCED WITH CARBON FIBER AND DISPERSION OF BISMUTH OXIDE (Bi_2O_3) NANOPARTICLES

Data de aceite: 01/11/2023

Pedro Marcio Munhoz

Nuclear and Energy Research Institute,
IPEN-CNEN, Radiation Technology
Center, Brazil
0000-0002-0072-7299

Fernando Codelo Nascimento

Nuclear and Energy Research Institute,
IPEN-CNEN, Radiation Technology
Center, Brazil
0000-0002-0076-7661

Leonardo G. A. Silva

Nuclear and Energy Research Institute,
IPEN-CNEN, Radiation Technology
Center, Brazil
0000-0002-7968-2117

Bruno Caravelas Gary

Nuclear and Energy Research Institute,
IPEN-CNEN, Materials Science and
Technology Center, Brazil
0000-0001-6486-2310

Wilson Aparecido Parejo Calvo

Nuclear and Energy Research Institute,
IPEN-CNEN, Radiation Technology
Center, Brazil
0000-0002-4316-8335

ABSTRACT: The aim of this study was to simulate gamma radiation attenuation using a polymer matrix composite of an epoxy (DGEBA) resin that was reinforced with carbon fiber cloth fabric and then dispersed with bismuth (III) oxide (Bi_2O_3) nanoparticles. The quantitative methodology was used for this simulation with the software Topas MC (version 3.7). The mass ratios of the bismuth (III) oxide nanoparticles in the composite were approximately 0.163, 0.244, 0.325 and 0.407. The photon energy in the simulation was 100 keV, typical X-ray energy in Medical Imaging (Diagnostic Radiography). The mass ratio of 0.407 and the polymer matrix composite at a thickness of 2.29 mm provided 89.03% attenuation of the photon energy. However, for the lead plate, a thickness of 0.34 mm was necessary for similar attenuation. Nonetheless, the fabrication process of a composite plate is easier than that of a lead plate. In conclusion, a composite of an epoxy polymer matrix, with bismuth (III) oxide dispersion, reinforced with carbon fiber, is an excellent option as compared to a lead plate. The composite plate can attenuate photon energy and does not present an acute or chronic danger to the environment or to health. Also, it is non-carcinogenic, and

does not cause reproductive toxicity, both clear advantages over lead. Finally, it should be noted that other applications of the composite would be production of an X-ray shield and aerospace industries, among others.

KEYWORDS: Epoxy composite, carbon fiber, bismuth oxide nanoparticles, gamma rays, radiation attenuation.

1 | INTRODUCTION

Currently, there has been growing interest in the use of bismuth and bismuth oxide for radiation protection applications, due to their unique properties, such as non-toxicity and high density. Radiation shielding materials incorporating Bi_2O_3 have been introduced to provide equivalent or greater attenuation compared to commercial lead-based or lead-free materials (e.g. BaTiO_3 , Bi_2O_3 , Br_2 , CaWO_4 , among others). Recently, polymers loaded with powdered metallic compounds, such as Bi_2O_3 , Gd_2O_3 , BaSO_4 , among others, have been developed to take advantage of their potentially useful attenuating capabilities [1], [2], [3], [4].

However, research that considers the mechanical properties of the composite and the radiation attenuation of bismuth trioxide are needed, but before of make a laminate it is better execute a simulation about radiation attenuation of the composite with a dispersion with Bi_2O_3 .

This study shows the results of simulation of radiation attenuation of the dispersion of the Bi_2O_3 in a composite with epoxy polymeric matrix, reinforced with carbon fiber.

2 | METHODOLOGY

For the simulation, the software Topas MC (version 3.7) [5] was used. It is a free distribution software, updated and user-friendly, which is based on the Monte Carlo method for simulating the interaction of radiation with matter [6]. There are several software that use the Monte Carlo methodology to simulate the interaction of radiation with material: ETRAN [7], ITS [8], EGS4 [9], PENELOPE [10], GEANT4 [11], MCNP6 [12], Topas [5], among others. Since all the mentioned software have the simulation results close to the results observed in practice, when photons are simulated.

For the simulation, a laminated plate measuring 100x100 mm was used, and the thickness of the laminate was 2.5, 5.0, 7.5 and 10 mm and such measurements were reproduced in practice and were determined due to the delimitation of the X-ray generator equipment [13].

The laminate of polymer matrix has 0.2 mm of carbon fiber. To finalize the thickness of the polymer matrix, epoxy resin is added with the dispersion of Bi_2O_3 to complete the total thickness of 2.5, 5.0, 7.5 and 10 mm. This separation between the polymeric matrix with dispersion and reinforcement is a simplification so that the simulation can be performed,

since, in practice, the carbon fiber and the polymeric matrix interact in a microscopic way.

To perform the simulation of radiation attenuation, provided by the composite object of this research study, the percentage of each chemical element present in such material must be calculated, such percentages are presented in the following paragraphs.

Furthermore, it is known that the average molar mass of the cross-linked epoxy resin is approximately equal to $115594 \text{ g}\cdot\text{mol}^{-1}$ [14]. That is, 24 chemical structures of epoxy resin bond with 4 chemical structures of amines thus forming the epoxy polymer matrix. This provides the following percentages: carbon 65.78%; oxygen 17.48%; Hydrogen 7.10% and nitrogen 0.14% [14], [15], [16]. Considering the dispersion percentages of bismuth trioxide (Bi_2O_3), object of this study and the composition for the production of the laminate, the percentages presented in Table 1 can be concluded.

Identification	Carbon (%)	Oxygen (%)	Hydrogen (%)	Nitrogen (%)	Silicic (%)	Bismuth (%)	Specific mass ($\text{g}\cdot\text{cm}^{-3}$)
A (Ep/FC)	73.40	18.37	6.92	0.14	1.17	16.26	1.21
Ep/FC/ Bi_2O_3	B1	58.72	18.43	5.54	0.11	0.94	16.26
	B2	51.42	18.44	4.85	0.10	0.79	24.40
	B3	44.04	18.49	4.15	0.08	0.70	32.53
	B4	36.74	18.51	3.46	0.07	0.56	40.66

Table 1. Mass composition of the chemical elements of the composite with a polymer matrix of epoxy resin with dispersion of bismuth trioxide (Bi_2O_3) particles, reinforced with carbon fiber fabric (estimate).

In Table 1, it can be seen that the formulation B4 with 40% by mass of Bi_2O_3 dispersion can increase by 288%, approximately, the specific mass of the composite without such dispersion. However, such specific mass still shows approximately 58.6% smaller in relation to lead ($11.34 \text{ g}\cdot\text{cm}^{-3}$). It is of the metals widely used for radiological protection for photons.

For the simulation, a gamma radiation source was used. The energy of such photons ranged from 50 to 125 keV. The radiation source is a circle of radius 30 mm. For the simulation of the gamma rays generation, a Gaussian distribution was used and 500 histories were generated for that simulation.

The photon energy detection occurred on the 2 largest surfaces of the laminate. The energy of the incident photons was detected on the surface closest to the radiation source, and on the surface furthest from the source. The energy of the photons that had already interacted was detected with the polymer composite.

3 | RESULTS AND DISCUSSIONS

The Fig. 1 shows a comparison between the attenuation, result of computer simulation, of a 10 mm thick plate of the composite object of this research study without dispersion of Bi_2O_3 (Fig. 1 (a)); with dispersion of such oxide with a mass fraction of 40% (Fig. 1 (b)) and with a lead plate of 0.5 mm of thickness, customarily used in Personal Protective Equipment – PPE, that use such metal (Fig. 1 (c)), all with photons of 100 keV energy.

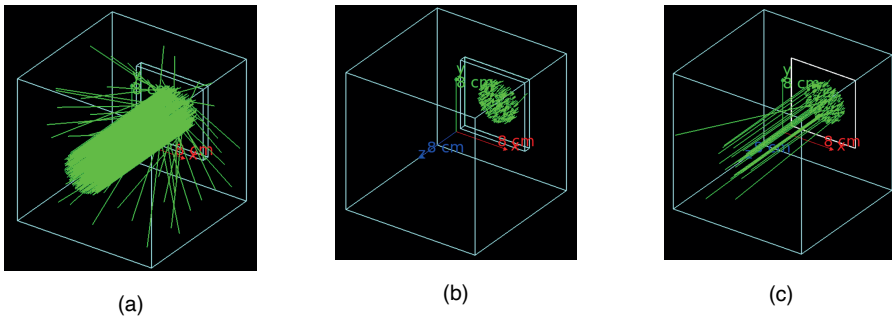


Fig. 1. Comparison between the attenuation, result of computer simulation, of a 10 mm thick epoxy composite reinforced with carbon fiber without (a) and with Bi_2O_3 dispersion (b), and 0.5 mm thick lead plate (c), all with photons energy of 100 keV.

The green lines shown in Fig. 1, represent the photon trajectory with 100 keV energy. It can be seen that the composite plate with Bi_2O_3 dispersion practically attenuates the photons, being more efficient than the lead plate.

An estimative of tenth value layers (TVL) and specific mass, is show in Fig. 2. The horizontal axis is the mass bismuth ration, and vertical left axis is the TVL and right is the specific mass.

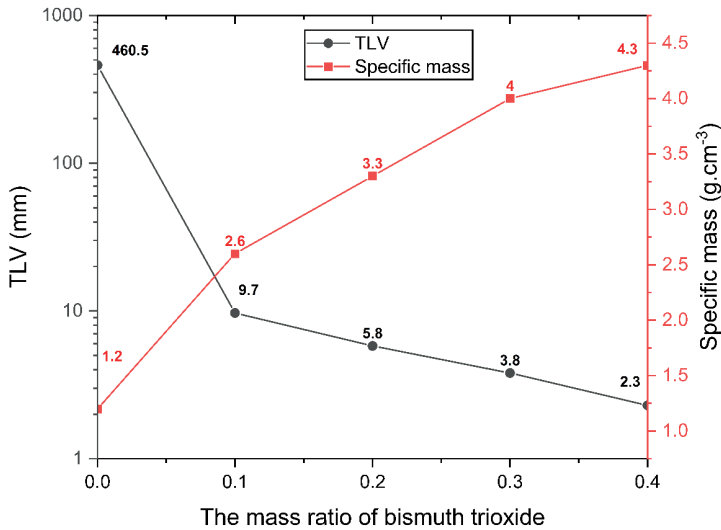


Fig. 2. Tenth value layers (TVL) and specific mass of composite epoxy with Bi_2O_3 dispersion and fiber plate in function of mass bismuth ration.

The mass ratios of the bismuth (III) oxide nanoparticles in the composite were approximately 0.163, 0.244, 0.325 and 0.407. The photon energy in the simulation was 100 keV, typical X-ray energy in Medical Imaging (Diagnostic Radiography). The mass ratio of 0.407 and the polymer matrix composite at a thickness of 2.29 mm provided 89.03% attenuation of the photon energy. However, for the lead plate, a thickness of 0.34 mm was necessary for similar attenuation.

The epoxy polymer composite with Bi_2O_3 dispersion and carbon fiber fabric, can be used as radiological protection for photons, such as X-rays, and such composite proves to be commercially attractive when compared to the lead (specific mass 11.34 g.cm^{-3}), metal customarily used for such radiological protection.

4 I CONCLUSIONS

The composite of an epoxy polymer matrix, with bismuth (III) oxide dispersion, reinforced with carbon fiber, is an excellent option as compared to a lead plate. The composite plate could attenuate photon energy and does not present an acute or chronic danger to the environment or to health. Also, it is non-carcinogenic, and does not cause reproductive toxicity, both clear advantages over lead. Therefore, the applications of the composite could be in the production of an X-ray shield and aerospace industries, among others.

The mass ratio of 0.407 (Bi_2O_3 nanoparticles) and the epoxy composite at a thickness

of 2.29 mm provided 89.03% attenuation of the photon energy (100 keV). So, the production of a polymer composite with an epoxy matrix and bismuth (III) oxide dispersion, reinforced with carbon fiber fabric is an innovation. In addition to the simulation, it is necessary to reproduce such a simulation in practice.

CREDIT AUTHOR STATEMENT

Pedro Marcio Munhoz: Conceptualisation; Methodology; Formal Analysis; Writing – original draft. **Fernando Codelo Nascimento:** Resources; Writing – review. **Leonardo G. A. Silva:** Resources; Writing – review. **Bruno Caravelas Gary:** Resources; Writing – review. **Wilson Aparecido Parejo Calvo:** Resources; Supervision; Writing – review.

DECLARATION OF COMPETING INTEREST

A competing interest statement is provided, even if the authors have no competing interest, it is necessary to declare as follow: The authors declare no conflict of interest.

REFERENCES

- [1] J.P. McCaffrey, F. Tessier, H. Shen, Radiation shielding materials and radiation scatter effects for interventional radiology (IR) physicians, *Medical Physics*. 39, p. 4537–4546, 2012.
- [2] G. Gershony, G. Weisz, M. Mooney, B. Katzen, Novel Lead-Free Lightweight Radiation Attenuating Material for Interventional Procedures., *Journal of Vascular and Interventional Radiology*. 22, 2011.
- [3] L.L.B.L. Marques, *Desenvolvimento de formulação com óxido de bismuto*, PhD Thesis, 2018.
- [4] Y. Yao et al, Investigation of gamma ray shielding efficiency and mechanical performances of concrete shields containing bismuth oxide as an environmentally friendly additive, *Radiation Physics and Chemistry*. 127, p. 188–193, 2016.
- [5] J. Perl et al, TOPAS: an innovative proton Monte Carlo platform for research and clinical applications, *Medical Physics*. 39, p. 6818–6837, 2012.
- [6] H. Yoriyaz, Método de Monte Carlo: princípios e aplicações em Física Médica, *Revista Brasileira de Física Médica*. 3, p. 141–149, 2009.
- [7] S.M. Seltzer, An overview of ETRAN Monte Carlo methods, *Monte Carlo Transport of Electrons and Photons*, p. 153–181, 1988.
- [8] J.A. Halbleib et al, ITS: the integrated TIGER series of electron/photon transport codes-Version 3.0, *IEEE Transactions on Nuclear Science*. 39, p. 1025–1030, 1992.
- [9] W.R. Nelson, H. Hirayama, D.W. Rogers, EGS4 code system, Stanford Linear Accelerator Center, Menlo Park, CA (USA), 1985.

- [10] F. Salvat, J.M. Fernandez-Varea, J. Baro, J. Sempau, PENELOPE, and algorithm and computer code for Monte Carlo simulation of electron-photon showers, 1996.
- [11] S. Agostinelli et al, GEANT4—a simulation toolkit, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment*. 506, p. 250–303, 2003.
- [12] J.T. Goorley et al, Initial MCNP6 release overview-MCNP6 version 1.0, Los Alamos National Lab. (LANL), Los Alamos, NM (United States), 2013.
- [13] M. Savi, D. et al, Study on attenuation of 3D printing commercial filaments on standard X-ray beams for dosimetry and tissue equivalence, *Radiation Physics and Chemistry*. 182, p. 109365, 2021.
- [14] C.A. Jacobs et al, Aplicação do método de Barrett ao estudo da reação de cura de sistema epóxi com hidroxipropilcelulose, *Salão de Iniciação Científica* (10.: 1998: Porto Alegre). Livro de Resumos. Porto Alegre: UFRGS, 1998. (<https://lume.ufrgs.br/handle/10183/88532>), accessed 8 august 2021.
- [15] K.I. Milagres, R.J.S. Rodriguez, *Formulação e caracterização de um material polimérico com memória de forma*, UNIVERSIDADE ESTADUAL DO NORTE FLUMINENSE DARCY RIBEIRO – UENF, CAMPOS DOS GOYTACAZES – RJ., 2015.
- [16] Guidechem, EINECS 220-666-8 *Isophorone diamine* 2855-13-2 Reach data, (2021). (<https://www.guidechem.com/products/2855-13-2.html>), accessed 17 september 2021.